




Geon™ Bold L5800 Alloy

PVC alloy for dark color capstock requiring premium weathering in both horizontal and vertical applications. Comes in satin gloss but may be customized for an application. Best option for lower heat build-up “jet black”.

LHB Black 2880												
Months	Arizona 45°				Ohio 45°				Florida 45°			
	Δ_L	Δ_a	Δ_b	Δ_E	Δ_L	Δ_a	Δ_b	Δ_E	Δ_L	Δ_a	Δ_b	Δ_E
0	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00
6	-0.26	-0.20	0.43	0.54	-0.23	0.48	-0.45	0.70	-0.52	0.07	-0.56	0.77
12	-0.96	-0.32	0.64	1.20	-0.46	0.43	-0.20	0.66	-1.09	0.63	-1.10	1.67
24	0.66	-0.27	0.52	0.88	-1.64	1.08	-0.56	2.04	-2.52	0.56	-0.61	2.65
36	-1.51	0.20	0.97	1.81	-1.16	0.41	-0.62	1.38	-1.32	0.93	-0.74	1.78
48												
60												

LHB Black 2880												
Months					Ohio Horiz							
	Δ_L	Δ_a	Δ_b	Δ_E	Δ_L	Δ_a	Δ_b	Δ_E	Δ_L	Δ_a	Δ_b	Δ_E
0					0.00	0.00	0.00	0.00				
9					-0.38	0.07	-0.06	0.39				
14					0.61	-0.02	-0.36	0.71				
24					-0.72	0.12	-0.28	0.78				
36					-0.27	0.02	-0.25	0.37				
48												
60												

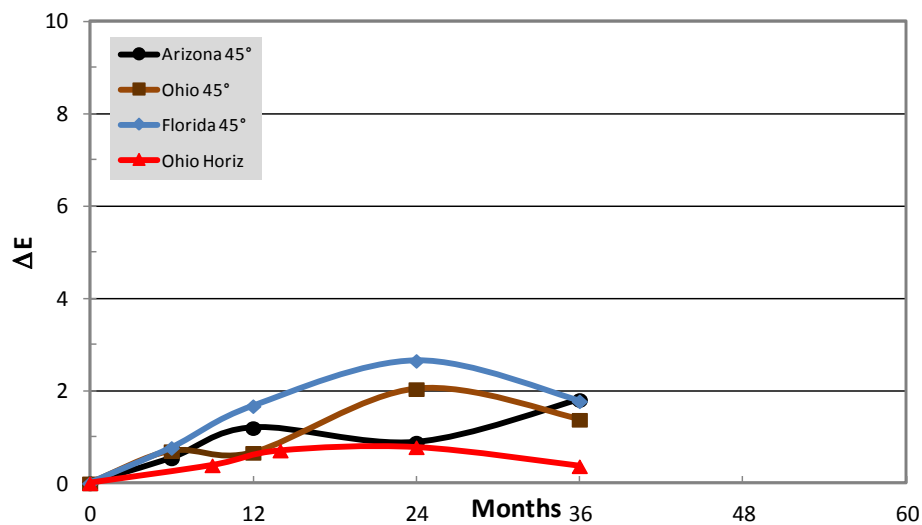

Notes:

Δ_L , Δ_a , Δ_b , and Δ_E are in Hunter units